

Spin state and phase competition in $\text{TbBaCo}_2\text{O}_{5.5}$ and the lanthanide series $\text{LnBaCo}_2\text{O}_{5+\delta}$ ($0 \leq \delta \leq 1$)

Hua Wu

Max-Planck-Institut für Physik komplexer Systeme, D-01187 Dresden, Germany

and Institute of Solid State Physics, Academia Sinica, 230031 Hefei, P. R. China

A clear physics picture of $\text{TbBaCo}_2\text{O}_{5.5}$ is revealed on the basis of density functional theory calculations. An antiferromagnetic (AFM) superexchange coupling between the almost high-spin Co^{3+} ions competes with a ferromagnetic (FM) interaction mediated by both p - d exchange and double exchange, being responsible for the observed AFM-FM transition. And the metal-insulator transition is accompanied by an xy/xz orbital-ordering transition. Moreover, this picture can be generalized to the whole lanthanide series, and it is predicted that a few room-temperature magnetoresistance materials could be found in $\text{LnBa}_{1-x}\text{A}_x\text{Co}_2\text{O}_{5+\delta}$ ($\text{Ln}=\text{Ho,Er,Tm,Yb,Lu}$; $\text{A}=\text{Sr,Ca,Mg}$).

PACS numbers: 75.50.-y, 71.20.-b, 71.15.Mb

Introduction. Materials with an interesting combination of electronic and magnetic properties are of current considerable interest, both from the basic points of view and as to their promising technological utilities. Well known one of this class is the colossal magnetoresistance (MR) manganite $R_{1-x}A_x\text{MnO}_3$ (R :rare earth; A :alkaline earth).¹ Its FM metallicity has been long explained in terms of the double exchange (DE) model,² where the spin of Mn e_g conduction electron is forced to be parallel to the localized t_{2g} spin due to strong on-site Hund coupling, and the effective electron hopping of the e_g electron is maximum when the neighboring Mn spins are parallel. Recently the DE model was modified by including a strong electron-phonon interaction stemming from the Jahn-Teller (JT) splitting of the Mn^{3+} ions.³ And late it was argued^{4,5} that owing to a considerable amount of O $2p$ holes in the charge-transfer⁶ (CT) oxides, p - d exchange also plays a crucial role in determining the T_C value and transport properties. The MR materials, especially those with a high MR value at room- T and low field have potential applications for magnetic memory and actuator devices.

Recently, the perovskite cobaltites of lanthanides $\text{LnBaCo}_2\text{O}_{5+\delta}$ ($0 \leq \delta \leq 1$) drew much attention, because they exhibit a few fascinating phenomena such as a metal-insulator (M-I) transition, an AFM-FM transition, and a giant MR effect near the AFM-FM transition temperature T_i .⁷⁻¹⁰ These intricate behaviors are closely related to an interrelation among the spin, charge, and orbital degrees of freedom of the Co ions. In most of the published experimental studies,⁷⁻⁹ the abundant electronic and magnetic properties were explained in terms of an intermediate-spin (IS) and/or a low-spin (LS) model for the Co ions. For example, it was suggested⁹ that upon decreasing T to $T_{\text{MI}} \approx 340$ K, $\text{TbBaCo}_2\text{O}_{5.5}$ transits from a Co^{3+} high-spin (HS) metallic phase to an IS and lattice-distorted b -axis $3x^2-r^2/3y^2-r^2$ orbital-ordered (OO) insulating state. In this OO IS model,

the observed FM state lying roughly between 260 and 340 K was ascribed to both the superexchange (SE) FM along the b -axis and the DE FM along the a -axis, and the lower- T AFM phase was ascribed to the overwhelming SE AFM.

However, it should be argued that such an OO IS state most probably leads to an AFM SE coupling along the c -axis as in the widely studied LaMnO_3 .¹¹ Consequently, the above explanation of the FM state is questionable, and thus the AFM-FM transition is somewhat hard to explain. In addition, there exists an intriguing issue¹² on the Co spin state in the isostructural $\text{Co}^{2+}/\text{Co}^{3+}$ charge-ordered (CO) systems YBaCo_2O_5 ¹³ and $\text{HoBaCo}_2\text{O}_5$ ¹⁴. Therefore, the Co spin state and origins of the phase transitions, being fundamental aspects of physics of the fascinating materials $\text{LnBaCo}_2\text{O}_{5+\delta}$, call for a further clarification.

In this paper, density functional theory¹⁵ (DFT) calculations for $\text{TbBaCo}_2\text{O}_{5.5}$ are exemplified to study the Co spin state and the phase competitions. The obtained results are distinct from the previous ones stated above, and a few fundamental evidences presented below clearly indicate that the original physics model⁹ of $\text{TbBaCo}_2\text{O}_{5.5}$ is invalid. Instead a new physics picture is revealed, and more importantly it can be generalized to the whole lanthanide series and leads to a theoretical prediction.

Computational details. Used in the following calculations are the 450-K paramagnetic (PM) structure and 270-K distorted one of $\text{TbBaCo}_2\text{O}_{5.5}$ measured by neutron diffraction experiments.⁹ Owing to a large difference between the Tb and Ba ionic radii, the O_4 basal squares of the alternate $\text{Co}(1)\text{O}_6$ octahedra and $\text{Co}(2)\text{O}_5$ pyramids along the b -axis move towards the smaller-Tb layer, leading to a bent Co-O-Co bond angle along the a - and b -axis.

The full-potential linearly combined atomic-orbital band method,¹⁶ based on the lo-

cal density approximation¹⁵ (LDA) to DFT and on-site Coulomb correlation correction (LDA+ U)¹⁷ to the localized Tb $4f$ and Co $3d$ states, is adopted in the following scalar relativistic calculations, where no spin-orbital coupling (SOC) is included.¹⁸ Tb $4f5p5d6s$, Ba $5p5d6s$, Co $3d4s$, and O $2s2p$ orbitals are treated as valence states. Hartree potential is expanded in terms of lattice harmonics up to $L=6$, and an exchange-correlation potential of von Barth-Hedin type is adopted.¹⁹ 125 special k points in irreducible Brillouin zone are used.

Results. In the LDA PM band structure, the partially occupied Tb³⁺ $4f$ bands are very narrow, contributing greatly to the density of states (DOS) at the Fermi level (E_F), as seen in Fig. 1. This high DOS peak is to be removed by a large Mott-Hubbard splitting. Note that the Co $3d$ and O $2p$ states consist of the most concerned valence bands ranging from -8 to 3 eV, on which other electronic states have a negligible influence. The Co(1)/Co(2) near-degenerate t_{2g} (xz, yz, xy) levels consist of a subgroup of narrow bands located between -1.5 and 0.5 eV, and the e_g ($x^2-y^2, 3z^2-r^2$) levels lie, respectively, above the corresponding t_{2g} ones by ≈ 1 and 0.7 eV (the latter as in YBaCo₂O₅¹²) due to a crystal-field (CF) splitting. The broad e_g bands ranging from -1 to 3 eV should be responsible for the metallic conductivity of TbBaCo₂O_{5.5} at the high- T PM phase.

In the LDA+ U calculation for the FM distorted structure, two choices of $U=8$ and 10 eV for the Tb $4f$ electrons result in only a rigid shift of the $4f$ levels and have no influence on the Co $3d$ and O $2p$ states. The corresponding Tb³⁺ ($4f^8$) spin moments of 5.91 and 5.94 μ_B suggest a full spin polarization. $U=5$ eV is used for the Co $3d$ electrons,¹² and a variance of $\Delta U=\pm 1$ eV leads to an insignificant change of the calculated results. It can be seen in Fig. 2(a.1-3) that the Co(1)/Co(2) majority-spin t_{2g} and e_g orbitals become completely occupied and nearly full-filled, respectively, thus giving an almost HS state

with an averaged Co spin moment of $3.4 \mu_B$ including a total contribution of $\approx 0.4 \mu_B$ from the coordinated oxygens. And the e_g orbitals couple to the O $2p$ ones and form wide conduction bands crossing E_F . Moreover, the near-degeneracy of the t_{2g} orbitals is lifted, and the minority-spin Co(1) xy and Co(2) xz orbitals are fully occupied, giving rise to an OO of the formal Co^{3+} ($3d^6$) ions.²⁰ Furthermore, the upper valence bands (lower conduction bands) are mainly of the O $2p$ (Co $3d$) character, leading to a classification of $\text{TbBaCo}_2\text{O}_{5.5}$ as a p - d CT oxide.⁶

It should be noted that the above LDA+ U metallic solution is closely related to both the assumed ideal FM ordering and the itinerant O $2p$ orbital character in this CT cobalt oxide which is something like the self-doped metallic ferromagnet CrO_2 .²¹ This result qualitatively accounts for a little abrupt decrease of the resistivity near T_i .⁹ While the observed insulating-like behavior of the so-called FM phase⁹ is probably ascribed to a spin canted structure²⁶ as suggested below. Moreover, the insulating ground state is exactly reproduced by the present AFM LDA+ U calculation for the distorted structure as seen in Fig. 2b, where the strongly suppressed bandwidths due to the carrier localization are evident. While the almost HS state and the xy/xz OO remain unchanged.

Discussions. It was theoretically found¹² that the pyramidal Co ions see a weak CF and remain in a HS state in YBaCo_2O_5 , and it is therefore not surprising that the pyramidal Co(2) ion almost takes the HS state in $\text{TbBaCo}_2\text{O}_{5.5}$. Also the octahedral Co(1) ion in $\text{TbBaCo}_2\text{O}_{5.5}$ almost takes a HS state due to a reduced CF. It has been experimentally revealed⁹ that strongly in contrast to a regular CoO_6 octahedron with a Co-O bond length of $\sim 1.9 \text{ \AA}$, the cobalt and two inequivalent planar oxygens of Co(1)O_6 in the 270-K phase move away from the ideal CoO_4 middle plane by 0.09, 0.23 and 0.33 $\text{\AA}$, respectively. The drastic deformation leads to the reduced CF splitting of $\approx 1 \text{ eV}$, and

consequently the HS state becomes energetically favorable.²² Owing to a nearly complete filling of the majority-spin e_g orbitals in the almost HS state, there is no freedom of the e_g orbitals for an OO. Instead the lattice distortion lifts the near-degeneracy of the t_{2g} orbitals and prefers the xy/xz OO (see discussions in Ref. 23). These fundamental evidences clearly indicate that the original model⁹ of the $3x^2-r^2/3y^2-r^2$ OO IS state is invalid for $\text{TbBaCo}_2\text{O}_{5.5}$. Instead it is proposed here that in this CT cobalt oxide, the Co^{3+} ions almost take a HS state with itinerant p - d hybridized holes of the e_g symmetry, and they exhibit the xy/xz OO.

Based on this proposal, a clear physics picture of $\text{TbBaCo}_2\text{O}_{5.5}$ is presented. A SE interaction (Ref. 24) between the almost HS Co^{3+} ions gives an AFM coupling. Owing to a significant O $2p$ orbital character of the p - d hybridized holes, the itinerant O $2p$ holes couple antiferromagnetically to the Co spins and align them ferromagnetically via the p - d exchange.^{4,25} Also the itinerant Co e_g holes mediate the FM coupling via DE.² In the low- T distorted structure of $\text{TbBaCo}_2\text{O}_{5.5}$, the OO is stabilized, and the p - d holes are strongly localized due to a polaron effect and thus the FM coupling is disfavored, and the AFM SE coupling is overwhelming instead. These effects account for the observed insulating AFM ground state.⁹ With increasing T below $T_{\text{MI}} \approx 340$ K, the p - d holes delocalize progressively but the OO survives as shown in Fig. 2a. As a result, a FM coupling becomes pronounced but the AFM coupling is inherent. Thus a spin canted structure²⁶ (rather than the so-called FM state⁹) appears in a relatively narrow range of T , which is considered to be the reason for the high resistivity with a little sudden drop near T_i .⁹ As the T increases further, the PM phase appears, the OO collapses, and the itinerant p - d holes result in a metallic behavior.

The present picture should be also applicable to other intermediate lanthanides of

this class, in view of a negligible influence of the strongly localized Tb^{3+} $4f$ electrons on the Co and O states as shown above. A relevant experimental evidence is that similar AFM-FM and M-I transitions were observed in the intermediate $\text{LnBaCo}_2\text{O}_{5+\delta}$ ($\text{Ln}=\text{Sm}, \text{Eu}, \text{Gd}, \text{Tb}, \text{Dy}$; $\delta \sim 0.5$).⁷ And in the intermediate lanthanides at $\delta=1$, a complete apical-oxygen occupation makes Co ions all octahedrally coordinated and thus to behave like the octahedral $\text{Co}(1)$ ions in $\text{TbBaCo}_2\text{O}_{5.5}$. As a result, they show a great similarity to those at $\delta \sim 0.5$ in the electronic and magnetic properties.^{8,7}

Moreover, this picture can be generalized to the whole lanthanide series as discussed below, by taking into account variances of both the spin state and the hole behavior, and a possible CO transition.

In the larger lanthanides, *e.g.*, $\text{Ln}=\text{La}$, Pr , and Nd , the decreasing difference between the Ln^{3+} and Ba^{2+} sizes leads to a relaxation of the CoO_4 basal square close to the ideal middle plane and therefore a weaker deformation of the Co-O polyhedra. As a result, the CF is enhanced and the Co HS state is disfavored. In particular, an IS state is most probably stabilized in $\text{LaBaCo}_2\text{O}_6$ (as in SrCoO_3 and $\text{LaSrCo}_2\text{O}_6$ ²⁵) by a strong p - d hybridization which is responsible for its FM metallicity⁸ via the p - d exchange and DE mechanisms. In addition, an IS-HS mixing state could appear in $\text{PrBaCo}_2\text{O}_{5+\delta}$ and $\text{NdBaCo}_2\text{O}_{5+\delta}$. Thus, the weak magnetization and semiconductive behavior observed in them⁸ can be reasonably ascribed to the coexisting IS FM metallicity and HS AFM insulating behavior.²⁶

In contrast, a larger CoO_4 displacement away from the middle plane is expected in the smaller lanthanides, *e.g.*, $\text{HoBaCo}_2\text{O}_5$, as well as YBaCo_2O_5 (See Refs. 9 and 13 for comparison). Consequently, the CF is strongly reduced, and the Co ions take a HS state and give a strong AFM SE coupling. The p - d holes are localized due to the strongly bent

Co-O-Co bonds. Thus, these smaller lanthanides should exhibit a pronounced AFM insulating behavior with high T_N as observed in $\text{HoBaCo}_2\text{O}_5$ ($T_N \sim 340$ K)¹⁴ and YBaCo_2O_5 ($T_N \sim 330$ K).¹³

Note that a CO transition is more likely realized in the intermediate and smaller lanthanides ($\delta=0,1$) with mixed-valence Co ions as observed in $\text{HoBaCo}_2\text{O}_5$ ¹⁴ and YBaCo_2O_5 ¹³, owing to the bent Co-O-Co bond angles and hence the reduced electron hoppings.^{10,12} This CO transition should be rather responsible for the M-I transition observed in the intermediate $\text{LnBaCo}_2\text{O}_6$.^{10,8}

As discussed above, with increasing T the intermediate $\text{LnBaCo}_2\text{O}_{5+\delta}$ ($\delta \sim 0.5,=1$) transit from an AFM insulator to a PM metal via an intermediate so-called FM state with a little sudden drop of high resistivity near T_i . An applied magnetic field will inhibit the AFM ordering of the Co spins but favor the FM coupling (and thus enhance the $p-d$ hole mobility), as was indicated by experiments⁸ that an external magnetic field lowers the T_i and makes broader the range of T for the FM state. As a result, the magnetic field changes the hole mobility in the intermediate lanthanides near the AFM-FM phase boundary more considerably than near the FM-PM or M-I phase boundaries, giving a giant negative MR near the T_i rather than near the T_C or T_{MI} .^{7,8} In contrast, the MR effect becomes weaker in the larger lanthanides which behave like a FM (semi)metal, and it disappears even in the smaller ones being almost an AFM insulator.⁷

Since a giant MR effect of the intermediate lanthanides appears near T_i , *e.g.*, 260K for $\text{TbBaCo}_2\text{O}_6$,⁸ some lanthanides of this class with a higher T_i value could be candidate room- T MR materials. In the sense, the smaller lanthanides, although intrinsically insulating, seem preferable through a modulation of the $p-d$ hole behavior. It can be reasonably postulated that a smaller- A ($A=\text{Sr,Ca,Mg}$) substitution for the Ba compo-

sition in the smaller lanthanides is a promising choice. Thus, the decreasing difference between the Ln and A sizes weakens the deformation of the Co-O polyhedra, and it leads to an enhancement of the $p-d$ hole itineracy at the expense of a little drop of the high T_i value. As a result, a few room- T MR materials could be found in $LnBa_{1-x}A_xCo_2O_{5+\delta}$ ($Ln=Ho,Er,Tm,Yb,Lu$; $A=Sr,Ca,Mg$) with a possibly optimized combination of both the T_i value and the $p-d$ hole itineracy. Moreover, such a doping in the intermediate lanthanides could increase their MR values.

Conclusion. Based on LDA and LDA+ U calculations for $TbBaCo_2O_{5.5}$, it has been proposed that the Co ions take an almost HS state with itinerant $p-d$ hybridized holes in the intermediate lanthanides $LnBaCo_2O_{5+\delta}$ ($Ln=Sm, Eu, Gd, Tb, Dy$; $\delta \sim 0.5, =1$), and most likely an IS state or an IS-HS mixing one in the larger ones ($Ln=La, Pr, Nd$; $\delta \sim 0.5, =1$) stabilized by a stronger $p-d$ hybridization, and a complete HS state with localized holes in the smaller $LnBaCo_2O_5$, *e.g.* $HoBaCo_2O_5$. Thus a general physics picture of the lanthanide series has been revealed that a competition between the HS AFM SE coupling and the FM interaction mediated by both $p-d$ exchange and DE due to the itinerant $p-d$ holes, and possible OO and/or CO transitions related to a lattice distortion, are responsible for the FM behavior of the larger lanthanides, and AFM-FM and M-I transitions in the intermediate ones, and the AFM insulating property of the smaller ones. Moreover, it is theoretically predicted that a few room- T MR materials could be found in $LnBa_{1-x}A_xCo_2O_{5+\delta}$ ($Ln=Ho,Er,Tm,Yb,Lu$; $A=Sr,Ca,Mg$).

Acknowledgments. The author thanks A.-m Hu and A. Yaresko for their valuable discussions. This work was cosponsored by Max Planck Society of Germany and National Natural Science Foundation of China.

REFERENCES

- ¹ W. E. Pickett and D. J. Singh, Phys. Rev. B **53**, 1146 (1996), and references therein.
- ² C. Zener, Phys. Rev. **82**, 403 (1951).
- ³ A. J. Millis *et al.*, Phys. Rev. Lett. **74**, 5144 (1995); **77**, 175 (1996).
- ⁴ G.-m. Zhao, Phys. Rev. B **62**, 11639 (2000).
- ⁵ H. L. Ju *et al.*, Phys. Rev. Lett. **79**, 3230 (1997).
- ⁶ J. Zaanen *et al.*, Phys. Rev. Lett. **55**, 418 (1985).
- ⁷ A. Maignan *et al.*, J. Solid State Chem. **142**, 247 (1999).
- ⁸ I. O. Troyanchuk *et al.*, Phys. Rev. Lett. **80**, 3380 (1998); Phys. Rev. B **58**, 2418 (1998).
- ⁹ Y. Moritomo *et al.*, Phys. Rev. B **61**, R13325 (2000).
- ¹⁰ Y. Moritomo *et al.*, Phys. Rev. B **58**, R13334 (1998).
- ¹¹ I. Solovyev *et al.*, Phys. Rev. Lett. **76**, 4825 (1996).
- ¹² H. Wu, Phys. Rev. B **62**, R11953 (2000).
- ¹³ T. Vogt *et al.*, Phys. Rev. Lett. **84**, 2969 (2000).
- ¹⁴ E. Suard *et al.*, Phys. Rev. B **61**, R11871 (2000).
- ¹⁵ P. Hohenberg and W. Kohn, Phys. Rev. **136**, B864 (1964); W. Kohn and L.J. Sham, Phys. Rev. **140**, A1133 (1965).
- ¹⁶ H. Wu *et al.*, J. Phys.: Condens. Matter **11**, 209 (1999).
- ¹⁷ V.I. Anisimov *et al.*, Phys. Rev. B **44**, 943 (1991).

¹⁸ Owing to a strong localization of the Tb $4f$ electron, its relativistic effect has a negligible influence on the most concerned Co $3d$ and O $2p$ states. In addition, a negligence of the Co SOC effect does not affect the present discussions on the Co spin state and orbital structure, since the strength of the SOC being commonly 0.01-0.1 eV is much weaker than the CF and Hund coupling.

¹⁹ U. von Barth and L. Hedin, J. Phys. C **5**, 1629 (1972).

²⁰ The minority-spin yz -band splitted off the majority-spin one by U also crosses E_F in the FM state due to broadened bandwidths caused by hybridizations with the itinerant O $2p$ orbitals.

²¹ M. A. Korotin *et al.*, Phys. Rev. Lett. **80**, 4305 (1998).

²² M. Zhuang *et al.*, Phys. Rev. B **57**, 10705 (1998).

²³ A strong JT distortion should be seen by the half-filled e_g orbitals with a $3x^2-r^2/3y^2-r^2$ OO as in LaMnO₃ (Refs. 1 and 11) where the difference between the ab intralayer Mn-O bond lengths is 0.27 Å. Strongly in contrast, the corresponding differences in TbBaCo₂O_{5.5} at the 270-K phase are only about 0.07 Å for Co(1)O₆ octahedra and 0.1 Å for Co(2)O₅ pyramids (Ref. 9). This much smaller difference signals a weak JT distortion seen by the t_{2g} electrons [Y. Tokura and N. Nagaosa, Nature **288**, 462 (2000)]. Moreover, the xy level is lowest among the Co(1) t_{2g} ones, owing to a shift of the Co(1) away from the ab basal square and close to one c -axis oxygen (Ref. 9). And the xz level is highest due to the a -axis Co(1)-O bond shorter than the elongated b -axis one. In Co(2)O₅ the distance between Co(2) and the ab O₄ square (the c -axis oxygen) is 0.32 Å on average (1.94 Å), and the a -axis Co(2)-O bond is longer than the shortened

b -axis one (Ref. 9). Thus the xz level is lowest and xy highest, according to the analyses in Ref. 12.

²⁴ P.W. Anderson, Phys. Rev. **115**, 2 (1959).

²⁵ R. H. Potze *et al.*, Phys. Rev. B **51**, 11501 (1995).

²⁶ A coexistence of FM and AFM probably leads to a canted spin structure [D. Akahoshi and Y. Ueda, J. Phys. Soc. Jpn. **68**, 736 (1999)] which disfavors a metallic conductivity. It also accounts for a relatively weak magnetization of $LnBaCo_2O_{5+\delta}$ even in the so-called FM state (Refs. 8 and 9), which, however, was previously ascribed to the Co LS state (Ref. 8).

FIGURES

FIG. 1. The LDA PM DOS. Fermi level is set at zero. The wide e_g bands and narrow t_{2g} ones are evident.

FIG. 2. (a.1-3) The LDA+ U Co $3d$ and O (Ref. 9) $2p$ DOS for the FM state. The solid (dashed) line denotes the majority (minority) spin. The almost HS and xy/xz OO state is evident, as well as itinerant $p-d$ holes. (b) Partial Co $3d$ DOS (for saving space) of the LDA+ U insulating state with b - and c -axis AFM ordering. The bandwidths will be further suppressed if the a -axis AFM ordering is also considered.

Fig.1--H. Wu

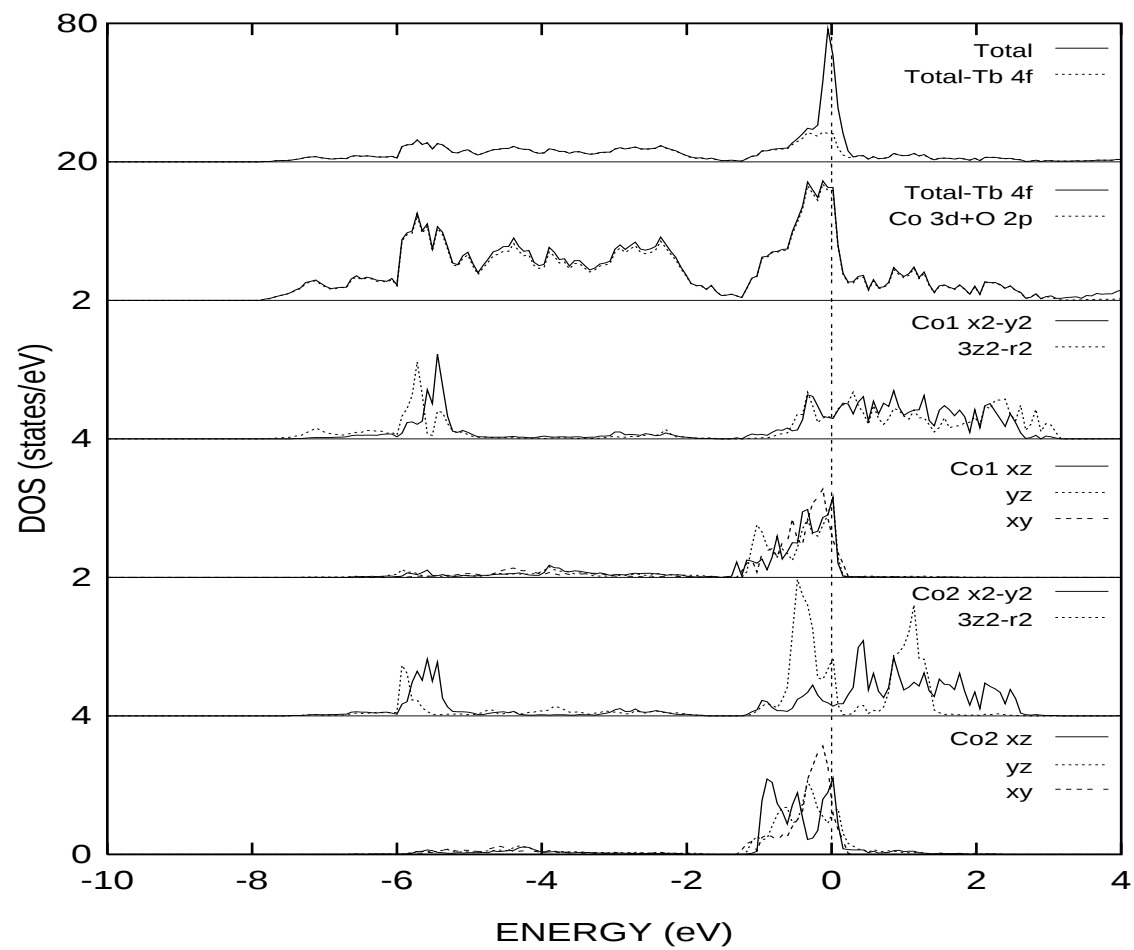


Fig.2--H. Wu

